

STELLITE 6

STELLITE™ 6 ALLOY

TECHNICAL DATA

TIG & OXY-ACETYLENE WELDING | MMA WELD DEPOSITION | MIG WELD DEPOSITION | PTA & LASER WELD DEPOSITION | HVOF & PLASMA SPRAY DEPOSITION

NOMINAL COMPOSITION (MASS %) AND PHYSICAL PROPERTIES

Co	Cr	W	C	Others	Hardness	Density	Melting Range
Base	27 – 32	4 – 6	0.9 – 1.4	Ni, Fe, Si Mn, Mo	36 – 45 HRC 380 – 490 HV	8.44 g/cm ³ 0.305 lb/in ³	1285 – 1410°C 2340 – 2570°F


STELLITE™ COBALT-BASED ALLOYS

consist of complex carbides in an alloy matrix. They are resistant to wear, galling, and corrosion and retain these properties at high temperatures. Their exceptional wear resistance is due mainly to the unique inherent characteristics of the hard carbide phase dispersed in a CoCr alloy matrix.

STELLITE™ 6 is the most widely used of the wear resistant cobalt-based alloys and exhibits good all-round performance. It is regarded as the industry standard for general-purpose wear resistance applications, has excellent resistance to many forms of mechanical and chemical degradation over a wide temperature range, and retains a reasonable level of hardness up to 500°C (930°F). It also has good resistance to impact and cavitation erosion. Stellite™ 6 is ideally suited to a variety of hardfacing processes and can be turned with carbide tooling. Examples include valve seats and gates, pump shafts and bearings, erosion shields, and rolling couples. It is often used self-mated.

CORROSION RESISTANCE

The typical electrode potential in sea water at room temperature is -0.25V (SCE). Like stainless steels, Stellite™ 6 corrodes primarily by a pitting mechanism and not by general mass loss in seawater and chloride solutions. Its mass loss in sea water is below 0.05mm per year at 22°C. More information regarding corrosion resistance can be provided on request.

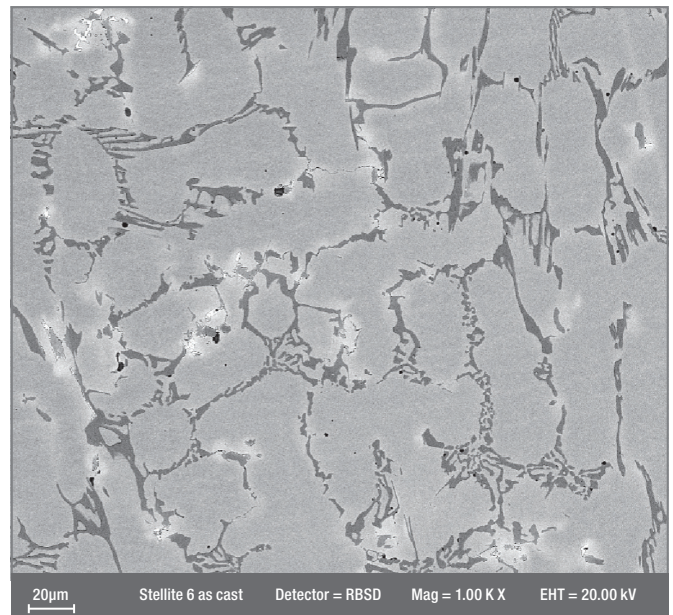

Scanning Electron Micrograph of Cast Stellite™ 6 at 1000x Magnification.



NOMINAL THERMAL EXPANSION COEFFICIENT (FROM 20°C/68°F TO STATED TEMPERATURE)

	100°C (212°F)	200°C (392°F)	300°C (572°F)	400°C (752°F)	500°C (932°F)	600°C (1112°F)	700°C (1292°F)	800°C (1472°F)	900°C (1652°F)	1000°C (1832°F)
µm/m.K	11.35	12.95	13.6	13.9	14.2	14.5	14.7	15.05	15.5	17.5
µ-inch/inch.°F	6.31	7.20	7.56	7.72	7.89	8.06	8.17	8.36	8.61	9.72

NOMINAL TENSILE PROPERTIES AT ROOM TEMPERATURE

	Ultimate Tensile Strength Rm		Yield Stress Rp (0.2%)		Elongation	Elastic Modulus	
	ksi	MPa	ksi	MPa	A(%)	psi	GPa
Castings	123	850	101.5	700	<1	30.3 x 10 ⁶	209
Stellite™ HS-6*	183.5	1265	109	750	3 – 5	34 x 10 ⁶	237

* "HS" = HIP-consolidated. Ref: *Ashworth et al. Powder Metal*. 1999, 42[3], pp. 243 – 249, and internal tests.

NOMINAL HOT HARDNESS (DPH) AS-CAST

20°C (68°F)	100°C (212°F)	200°C (392°F)	300°C (572°F)	400°C (752°F)	500°C (932°F)	600°C (1112°F)	700°C (1292°F)	800°C (1472°F)	900°C (1652°F)
410	390	356	345	334	301	235	155	138	95

THERMAL AND ELECTRICAL PROPERTIES

	Approximate Value at Room Temperature	
Thermal Conductivity	14.82 W/m.K	102.7 Btu-in/hr/ft ² /°F
Electrical Resistivity	106 µ-ohm.cm	41.7 µ-ohm.inch

PRODUCT FORMS AND CROSS REFERENCE SPECIFICATIONS

Stellite™ 6 is available as welding wire, rod, powder, and electrodes, finished castings and P/M parts. Kennametal Stellite™ also offers hardfacing services. A separate brochure is available for the wrought forms of this alloy, namely Stellite™ 6B and Stellite™ 6K. Stellite™ 6 can be supplied to the following specifications:

SPECIFICATION	PRODUCT FORM	SPECIFICATION	PRODUCT FORM
UNS R30006	Rod, Castings	AWS A5.21 / ASME BPVC IIC SFA 5.21 ERCoCr-A	Rod
UNS R30106	P/M Parts	AWS A5.21 / ASME BPVC IIC SFA 5.21 ERCCoCr-A	Wire
UNS W73006	Electrode	AWS A5.13 / ASME BPVC IIC SFA 5.13 ECoCr-A	Electrode
UNS W73036	Wire		
UNS 5387	Castings		
AMS 5788	Rod, Wire		

Kennametal Stellite™ manufactures sophisticated alloys in the form of castings, powders, coatings, consumables, and machined parts that resist wear, corrosion, and abrasion. Information provided in this document is intended only for general guidance about Kennametal Stellite™ products and is the best information in our possession at the time. Product users may request information about their individual use of our products, but Kennametal Stellite™ does not warrant or guarantee this information in any way. Selection and purchase of Kennametal Stellite™ products is the sole responsibility of the product user based on the suitability of each use. Individual applications must be fully evaluated by the user, including compliance with applicable laws, regulations, and non-infringement. Kennametal Stellite™ cannot know or anticipate the many variables that affect individual product use and individual performance results may vary. For these reasons, Kennametal Stellite™ does not warrant or guarantee advice or information in this document, assumes no liability regarding the same, and expressly disclaims any warranty of any kind, including any warranty of fitness for a particular purpose, regarding the same.

EUROPEAN SALES OFFICES

Kennametal Stellite Unit 3, Birch Kembrey Business Park Swindon SN2 8UU UK Phone: 44.1793.498500 Fax: 44.1793.498501	Kennametal Stellite Zur Bergpflege 51 – 53 56070 Koblenz Germany Phone: 49.261.80.88.0 Fax: 49.261.80.88.35	Kennametal Stellite Via G. Di Vittorio, 24 20090 Pieve Emanuele Milan Italy Phone: 39.02.907871 Fax: 39.02.90787 231
---	---	---

E-mail: europesales.stellite@kennametal.com

AMERICAS SALES OFFICE

Kennametal Stellite
1201 Eisenhower Drive N
Goshen, Indiana 46526
USA
Phone: 1.574.534.2585
Fax: 1.574.534.3417

E-mail: americasales.stellite@kennametal.com



www.kennametal.com/stellite